

# EXTENDED NON-DESTRUCTIVE TESTING OF COMPOSITE BONDS

Optimum bonding solutions for light-weight aircraft structures




## PROJECT OVERVIEW

ENCOMB provided advanced non-destructive testing (NDT) methods for pre and post-bond inspection of CFRP aircraft structural components in order to establish a reliable quality assurance concept for adhesive bonding. State-of-the-art NDT techniques were screened and the most suitable ones were further developed and adapted to important application scenarios with regard to aircraft manufacturing and in-service repair.

## IDENTIFICATION OF FACTORS INFLUENCING ADHESIVE BOND QUALITY

Five application scenarios were identified to be of primary importance for the aircraft manufacturers along with the requirements for extended NDT technologies applying to each scenario.

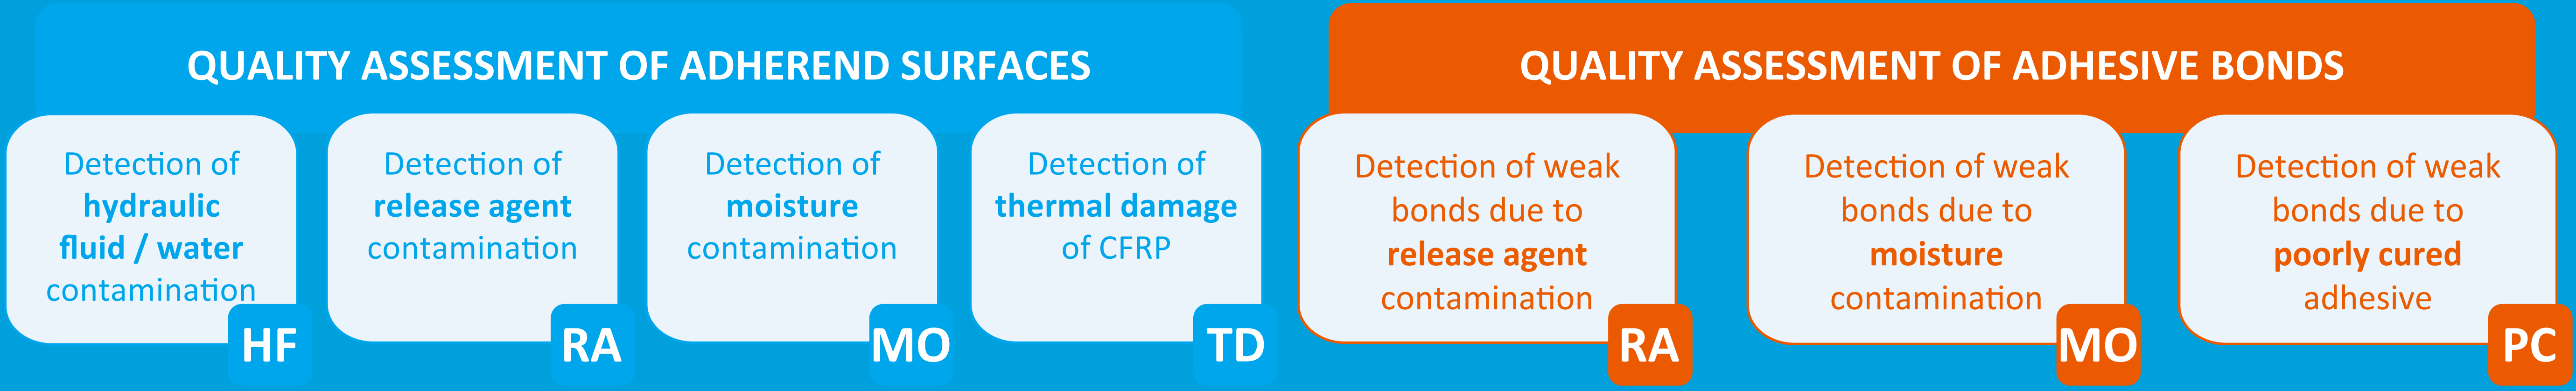

## QUALITY ASSESSMENT OF ADHEREND SURFACES & ADHESIVE BONDS

Pre and post-bond quality assessment was based on the physico-chemical characterisation of adherend surfaces and adhesive bonds. To this aim reference samples were manufactured for the development of methods. Strict requirements in terms of raw materials, geometry, manufacturing process, adherend surface treatment and bonding process were followed throughout the manufacturing process to ensure minimal deviation in terms of quality of the produced samples and enhance the reliability of the tests.

Adherend surfaces were characterised with conventional laboratory analysis methods (spectroscopic and optical techniques, contact angle measurements) to analyse their physico-chemical properties resulting from sample preparation.

Adhesively bonded samples were characterised with conventional NDT techniques (ultrasonic and x-ray inspection,  $\mu$ -CT) to analyse their structural integrity resulting from sample preparation.

Mechanical tests were performed on the adhesively bonded samples in order to determine the influence of sample treatment on their mechanical performance. These tests comprised interlaminar fracture toughness and double-lap shear tests.

## SCREENING, ADAPTATION & VALIDATION OF ADVANCED NDT TECHNIQUES

Advanced NDT technologies for the detection of selected physico-chemical properties of CFRP adherend surfaces and the quality of the adhesive bonds were identified, verified, developed, adapted, and validated for their potential to comply with the application scenarios and requirements.

	METHOD	PARTNER	Step 1				Step 2				VALIDATION	
			Scenarios				Potential for detection of					
			RA	MO	HF	TD	RA	MO	HF	TD		
Adherend surface quality	X-ray fluorescence spectroscopy	IFAM	-	-	✓	-	used as reference methods					
	Infrared spectroscopy	IFAM	-	-	✓	✓						
	Reflectometry / Ellipsometry	IFAM	-	-	-	-						
	Laser scanning vibrometry*	IMP PAN	✓	✓	✓	✓	○	●	○	○	Fail	
	Optically stimulated electron emission	IFAM	✓	-	✓	✓	●	●	●	●	Pass	
	Infrared spectroscopy	RECENTDT	✓	✓	✓	✓	●	●	●	●	Pass	
	Aerosol wetting test	IFAM	✓	-	✓	✓	●	○	●	●	Fail	
	Portable Handheld FTIR spectroscopy	AGILENT	✓	✓	✓	✓	●	●	●	●	Pass	
	Laser induced breakdown spectroscopy	IFAM	✓	-	✓	-	●	○	●	○	Pass	
	THz/GHz reflectometry	IRE NASU	✓	✓	✓	-	●	●	●	○	Pass	
	Optical fibre sensors*	EPFL	-	✓	✓	-	N/T	●	●	N/T	N/T	
	Electrochemical impedance spectroscopy*	IFAM	-	✓	✓	-	N/T	●	N/T	N/T	N/T	
	Electronic nose technology	ENEA	-	-	✓	-	●	●	●	N/T	Fail	
	Dual-band active thermography	IZFP	-	-	-	-	○	●	●	●	Fail	
	Laser induced fluorescence	IMP PAN	-	-	-	✓	○	○	●	●	Fail	
THz technology	RECENTDT	-	-	-	-							
Optical coherence tomography	RECENTDT	-	-	-	-							
Adhesive bond quality	TECHNIQUE	PARTNER	Step 1			Step 2			Potential to detect weak bonds caused by			VALIDATION
	Scenarios											
	RA	MO	PC	RA	MO	PC						
	Active thermography using ultrasonic excitation	EADS-D	-	-	-							
	Terahertz technology	IRE NASU	-	-	-	○	○	○		N/T		
	Linear Ultrasound	UnivBris	✓	-	-	●	N/T	○		Uncertain		
	Nonlinear ultrasound	UnivBris	✓	-	-	●	N/T	○		Pass		
	LASAT technique	CNRS	✓	-	-	●	●	●		Pass		
	Laser ultrasound	RECENTDT	-	-	-	○	○	○		Fail		
	Active thermography using optical excitation	IZFP	✓	✓	-	●	●	N/T		Uncertain		
	Laser scanning vibrometry*	IMP PAN	-	✓	-	○	●	●		Fail		
	Electromechanical impedance*	IMP PAN	✓	✓	✓	●	●	●		Fail		
	Ultrasonic frequency analysis	EADS-D	-	✓	-	●	●	○		Pass		
	Laser ultrasound	EADS IW F	-	-	-	○	●	●		Fail		
	Active thermography (for T <sub>g</sub> analysis)	IFAM	-	-	-							

NDT method development was carried out in two steps:

- a. The first comprised a simple comparison of treated samples with a clean reference for all scenarios as a rough screening for principal suitability of the NDT technologies.
- b. The second step was dedicated to optimising those technologies with demonstrated suitability by means of samples with different contamination levels down to threshold levels of insignificant impact on bond strength.

✓ : Clear detection of contaminant, differentiable from reference surface state  
- : No differentiation from reference state  
● : High  
● : Low  
○ : No  
N/T : Not Tested  
\* : With Structure Integrated Sensor

## DEVELOPMENT OF A QUALITY ASSURANCE CONCEPT

## IN-LINE AND IN-SERVICE QUALITY CONTROL

### WHO WE ARE:



### COORDINATED by:



Fraunhofer Institute for Manufacturing Technology and Advanced Materials IFAM  
Wiener Strasse 12 | 28359 Bremen | Germany  
Contact  
Dr. Michael Hoffmann | michael.hoffmann@ifam.fraunhofer.de



This project received funding from the European Union's Seventh Framework Programme for research, technological development and demonstration under grant agreement no 266226.

Endorsed by:



Designed by Fraunhofer IFAM and EASN-TIS